

Charge order in $\text{La}_{1.8-x}\text{Eu}_{0.2}\text{Sr}_x\text{CuO}_4$ studied by resonant soft X-ray diffraction

J. Fink,^{1,2} E. Schierle,³ E. Weschke,³ J. Geck,⁴ D. Hawthorn,⁴ H. Wadati,⁴

H.-H. Hu,⁵ H. A. Dürr,¹ N. Wizen,² B. Büchner,² G.A. Sawatzky,⁴

¹ BESSY, Albert-Einstein-Strasse 15, 12489 Berlin, Germany

² Leibniz-Institute for Solid State and Materials Research Dresden, P.O. Box 270116, D-01171 Dresden, Germany

³ Hahn-Meitner-Institut Berlin c/o BESSY, Albert-Einstein-Str. 15, D-12489 Berlin, Germany

⁴ Department of Physics and Astronomy, University of British Columbia,
6224 Agricultural Road, Vancouver, BC, V6T 1Z1 Canada

⁵ II. Physikalisches Institut, Universität zu Köln, Zùlpicher Strasse 77, D-50937 Köln, Germany

(Dated: May 28, 2008)

Resonant soft X-ray scattering with photon energies near the O K and the Cu L_3 edges was used to study charge ordering in the system $\text{La}_{1.8-x}\text{Eu}_{0.2}\text{Sr}_x\text{CuO}_4$ as a function of temperature for $x = 0.125$ and 0.15 . From the superstructure diffraction intensities a charge ordering with a doping dependent wave vector is derived which is in this system well below the transition temperature of the low-temperature tetragonal phase but well above the onset of spin ordering. This indicates that charge ordering is the primary driving force for the formation of stripe-like phases in two-dimensional doped cuprates. Analysis of the lineshape of the scattered intensity as a function of photon energy yields evidence for a high hole concentration in the stripes.

PACS numbers: 61.05.cp, 71.45.Lr, 74.72.Dn, 75.50.Ee

In the doped cuprates there exists a complex interplay between lattice, charge and spin degrees of freedom yielding several phases in a narrow concentration range: the antiferromagnetic insulating phase, the high- T_c superconducting phase, the pseudo-gap region and charge- and spin-ordered phases. The latter are usually divided into checkerboard phases and stripe-like phases. The stripe-like phase in which antiferromagnetic antiphase magnetic domains are separated by periodically spaced domain walls to which the holes segregate was first predicted from Hartree-Fock analysis of the single-band Hubbard model [1]. Fluctuating stripe-like order of spins in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ (LSCO) near $x = 1/8$ has been inferred from neutron scattering showing incommensurate magnetic correlations [2]. In $\text{La}_{1.875}\text{Ba}_{0.125}\text{CuO}_4$ (LBCO) superconductivity is strongly suppressed and a low-temperature tetragonal (LTT) phase appears which stabilizes a static stripe-like order due to the corrugated pattern of the in-plane lattice potential [3]. A static stripe-like order of the Cu spins has also been detected in $\text{La}_{1.6-x}\text{Nd}_{0.4}\text{Sr}_x\text{CuO}_4$ (LNSCO) by neutron scattering. In these compounds the corrugation of the CuO_2 plane is more pronounced due to the smaller ionic radius of Nd compared to La [4]. Replacing Nd by even smaller Eu ions, a phase diagram of the system $\text{La}_{1.8-x}\text{Eu}_{0.2}\text{Sr}_x\text{CuO}_4$ (LESCO) has been proposed based on μSR experiments [5]. There the magnetic stripe order almost completely replaces the superconducting range between $x = 0.08$ and 0.2 . Only above $x \approx 0.2$ superconductivity could be detected in a narrow concentration range.

Using neutron scattering [4] and non-resonant X-ray scattering [6], the ordering of the charges can be only monitored indirectly by the associated lattice distortion. The reason for this is that neutron and X-ray diffrac-

tion are mainly sensitive to the nuclear scattering and the core electron scattering, respectively. More direct information on the charge modulation in cuprates can be obtained by resonant soft X-ray scattering (RSXS) using photon energies at the O K and the Cu L edge [7, 8]. In particular at the threshold of the O K level the form factor for a charge carrier is enhanced by a factor of 82 [8]. Near the Cu L edge there is a strong enhancement of the form factor as well, but mainly lattice distortions are probed which may be caused by charge modulations [9]. In the high- T_c superconductor LSCO ($x = 0.15$) no static stripe-like modulation of the charge carriers could be detected by RSXS [7] while in the compound LBCO ($x = 1/8$) a strong modulation of the charge carriers has been observed in the range below the LTT phase transition temperature $T_{LTT} = 55$ K. We emphasize a striking feature of all investigations of stripe-like charge and spin order in this system: the ordering seems to be of cooperative nature, i.e. charge and spin order show similar temperature dependence and the appearance of the charge order at T_{CO} and a spin ordered state at T_{SO} is found very close to T_{LTT} [3]. In LNSCO with $x = 0.125$ and $T_{LTT} = 70$ K, on the other hand, lattice distortions due to charge ordering have been detected at $T_{CO} = 62$ K and spin order at $T_{SO} = 54$ K [10]. The three transition temperatures in this system are slightly separated and there is an indication that charge order may be more important for the formation of a stripe-like order than spin order. In the compounds LESCO, which is the focus of this study, $T_{LTT} = 125$ K and $T_{SO} = 45$ K, derived from neutron scattering [11], are distinctly different. The possible appearance of a separate charge and spin ordering should therefore be readily observable in this system.

In this contribution we have determined charge ordering directly by means of RSXS in a second system besides

LBCO, namely in LESCO. From a lineshape analysis of the superstructure diffraction intensity as a function of photon energy across the O K resonance, we infer the existence of a high doping concentration per Cu site in the hole stripes. Furthermore, it is shown that the incommensurate charge ordering wave vector exhibits a doping dependence corresponding to that observed for spin order. In contrast to the previous RSXS study of LBCO, we find a modulation of the charge carrier density in a large temperature range without spin order. These findings clearly show that the primary driving force for stripe formation is the charge channel.

The RSXS experiments were performed at the BESSY undulator beam line UE 46-PGM operated by the Hahn-Meitner Institut Berlin, working with vertically polarized photons in a horizontal scattering geometry. A two-circle UHV diffractometer was equipped with a continuous flow He cryostat. The detector was a silicon diode which had an angular acceptance of 0.8° in the scattering plane and 4° perpendicular to it. LESCO single crystals were grown using the traveling solvent floating zone method. X-ray diffraction, ^{63}Cu NMR spectroscopy and magnetic susceptibility measurements yielded for both concentrations a first order phase transition at $T_{LTT} = 125$ K [12]. The single crystals were cleaved parallel to the (001) surface in air shortly before the transfer to the scattering chamber. At a photon energy of 1100 eV the (002) peak could be reached which was used together with the superstructure peaks to orient the sample.

In Fig. 1 we present a comparison of X-ray absorption spectroscopy (XAS) measurements using the fluorescence method with the photon-energy dependence of the superstructure intensities near the O K and the Cu L_3 edges for a LESCO ($x = 0.125$) single crystal at a temperature $T = 6$ K. We denote the wave vector $\mathbf{Q} = (2\pi h/a, 2\pi k/b, 2\pi l/c)$ with Miller indices (h, k, l) where in the LTT phase $a = b = 3.79$ Å and $c = 13.14$ Å for $x = 0.125 - 0.15$. In accordance with previous electron energy-loss spectroscopy (EELS) and XAS studies [13, 14] we see (Fig. 1 (a)) at 528 eV transitions into the O $2p$ doped hole states in the conduction band (CB) and at 530 eV transitions into the Cu $3d$ upper Hubbard band (UHB) hybridized with O $2p$ states. The RSXS intensity of the (0.23, 0, 1) superstructure reflection displays a strong resonance at the energy of the doped hole states, indicating a strong density modulation of the charge carriers. There is also a weaker resonance at the UHB of the O K edge which has been related to a modulation of correlation effects [8]. For the Cu L_3 edge, transitions into the Cu $3d$ hole states are observed. The shoulder near 931 eV is usually ascribed to Cu $3d^9\bar{L}$ ligand-hole states which increases with increasing doping concentration. The superstructure peak also shows a strong resonance at the white line of the Cu L_3 edge (see Fig. 1 (b)).

In order to glean information about the electronic structure of the stripes, we have modeled the lineshape of

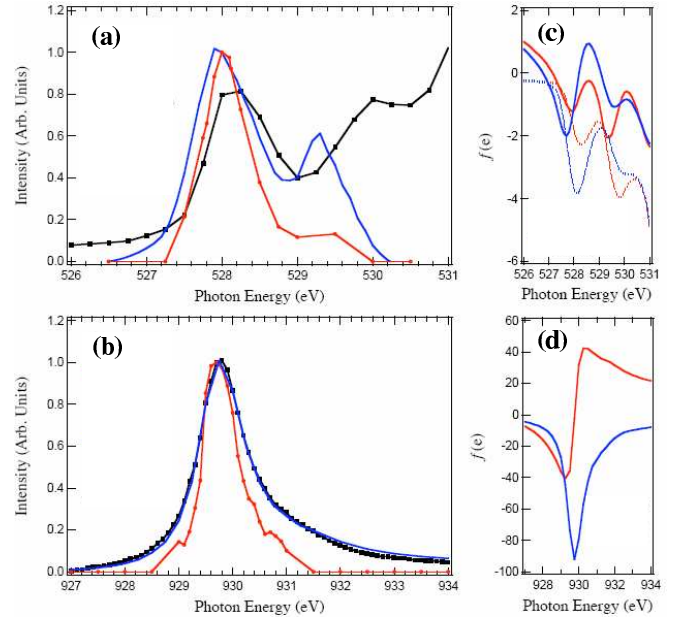


Figure 1: (color online). (a), (b): the resonant scattering intensity (red) as a function of photon energy through the O K [Cu L_3] absorption edge for the stripe superstructure peak. Data were taken near the O K [Cu L_3] for $l = 0.75$ [1.6]. Also shown is the X-ray absorption spectrum (black) and the calculated scattering intensity (blue). (c): the real (solid line) and the imaginary (dotted line) part of the atomic form factor f at the O K edge of LSCO for $x = 0.07$ (red) and $x = 0.15$ (blue). (d): the real (red) and the imaginary part of the atomic form factor f at the Cu L_3 edge of LSCO for $x = 0.125$.

the scattered intensity at both the O K and Cu L edges. In Figs. 1 (a) and (b) we also present the results of these calculations. In general, the scattering intensity, I_{sc} , will be given by

$$I_{sc}(\mathbf{Q}) \propto \left| \sum_j f_j(E, x + \delta x_j) e^{-i2\pi\mathbf{Q} \cdot (\mathbf{r}_j + \delta \mathbf{r}_j)} \right|^2, \quad (1)$$

where δx_j is the change in local hole doping away from x arising from an electronic ordering and $\delta \mathbf{r}_j$ is a change in the lattice position due to a lattice distortion. Similar to the treatment of the RSXS data of LBCO [8] at the O K edge we assume that the predominant contribution to the scattering is from electronic ordering and neglect the lattice distortions ($\delta \mathbf{r}_j = 0$). XAS measurements on LSCO at different Sr doping levels [15] allows us to determine $f_j(E, x + \delta x_j)$ by making use of the proportionality between $\Im(f_j)$ and the X-ray absorption, followed by a Kramers-Kronig transformation to obtain $\Re(f_j)$.

The precise structure of the stripe order and magnitude of the charge modulation – whether there is a sinusoidal variation in charge modulation or whether we have the extreme case of half-filled charge stripes separated by undoped anti-ferromagnetic domains – will de-

termine the appropriate expansion of Eq. (1). At the O K edge the X-ray absorption [14], and subsequently the atomic scattering form factor, varies roughly linear with doping for x less than ≈ 0.2 so that $f_j(E, x + \delta x_j) = f(E, x) + (\Delta f(E, x)/\Delta x)\delta x_j$. Assuming that this linear expansion is valid, the lineshape of the superstructure intensity only depends on $\Delta f(E, x)/\Delta x$ and not on other details of the stripe order. As such we can use XAS measurements at $x = 0.07$ and 0.15 from [15] to determine $f(E, x = 0.07)$ and $f(E, x = 0.15)$ (shown in the Fig. 1 (c)) and calculate $I_{sc,OK} \propto |\Delta f(E, x)/\Delta x|^2$, as shown in Fig. 1 (a). This calculation captures the measured peak positions correctly, but produces two unexpected discrepancies: similar to the case of LBCO [8] the measured lineshape is narrower than calculated and, most strikingly, the second peak at 529.3 eV is too large.

At the Cu L edge, the intensity of the superstructure reflection is associated with structural distortions [9] In the case $\delta x_j = 0$, the energy dependent lineshape is given by $I_{sc,CuL} = |f_{Cu}|^2$. The corresponding results of the Kramers-Kronig analysis using Cu L_3 XAS results from the literature [15, 16] are shown in Figs. 1 (b) and (d). The calculated RSXS lineshape is almost identical to the XAS data but the width is much larger than that of the resonant scattering intensity.

However, in the calculations presented above several assumptions have been made which could influence the calculated linewidths. For instance, it could be insufficient to consider only a purely structural modulation for the RSXS at the Cu L_3 edge. Regarding the O K edge, it may be that the essentially ionic (local) description above is not a good approximation for the band-like states probed at the O K edge. It is also not obvious whether or not the form factors deduced from XAS measurements outside the stripe phase provide a good description for the scattering centers in the stripe ordered phase.

Another assumption made for the O K edge is the strict linearity of the form factor with respect to x . The small scattering intensity for the UHB relative to the CB may be explained by a deviation from the linear concentration dependence of the absorption coefficient for the two bands. For $x < 0.2$ EELS and XAS experiments [13, 14, 15, 16] as well as theoretical calculations for strongly covalent charge transfer insulators [17] indicate that the X-ray absorption and hence in a first approximation also the form factor for the CB and the UHB is proportional to $2x$ and $1-x$, respectively. Based on this, the intensity ratio $I_{CB}/I_{UHB} = |(\Delta f(E, x)/\Delta x)_{CB}/(\Delta f(E, x)/\Delta x)_{UHB}|^2 = 4$ in fair agreement with the calculated curve in Fig. 1 (a). On the other hand, the cited experiments indicate at higher x -values a strong reduction of the linear decrease of the UHB absorption. Thus the strong reduction of the measured scattering intensity for the UHB can be readily explained by a deviation from the linear model used in

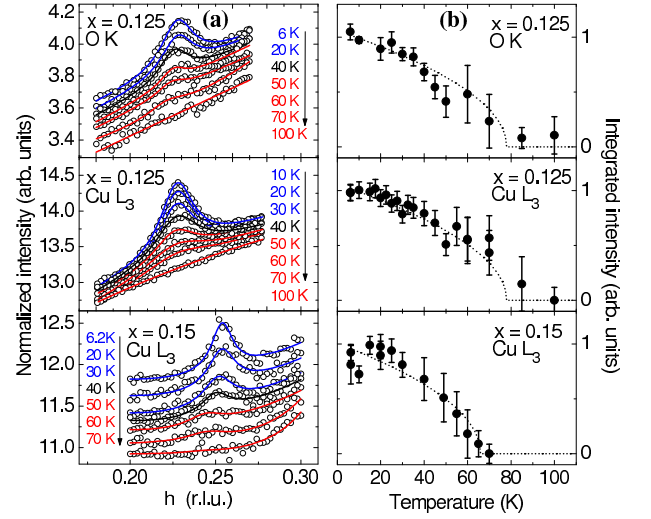


Figure 2: (color online). (a): temperature dependence of h scans along $(h, 0, l)$ showing superstructure reflections of LSCO ($x = 0.125$ and 0.15) using O K ($l = 0.75$) and Cu L_3 ($l = 1.6$) photon energies. Points depict RSXD data, the solid lines represent fits to the data. The fit to the data close to T_{SO} is marked by a black line to highlight the existence of charge order above this temperature. (b) temperature dependence of the intensities of the superstructure reflections shown in (a) normalized to the intensity at $T = 6$ K. The dotted line is a guide to the eyes ($\propto (T_c - T)^{1/2}$)

the calculations together with a high doping concentration per Cu site ($x \gg 0.2$) within the hole stripes in agreement with a previous analysis for LBCO [8].

In Fig. 2 (a) we present h -scans of the superstructure reflections with photon energies near the O K edge (528.0 eV) and the Cu L_3 edge (929.7 eV) for $x = 0.125$ and for photon energies at the Cu L_3 edge for $x = 0.15$. Typical signal to background ratios were near 0.05. For $x = 0.15$ and O K photon energies there might be an indication of a small superstructure reflection near $(0.25, 0, l)$ at low temperatures but a clear peak could not be resolved (data not shown). The scans presented in Fig. 2 (a) could be readily fitted by a Lorentzian plus a polynomial background. Besides the scans shown in Fig. 2 (a) we have also measured various scans for different l values. In agreement with previous studies of LBCO ($x=1/8$) [8] we do not observe a pronounced variation of the diffraction intensities within the small accessible l -range at the resonant energies. This indicates rather short coherence lengths along the c -axis which are shorter than 2 times the lattice constant c . The intensities of the superstructure peaks, as derived from the area of the Lorentzians, as a function of temperature are shown in Fig. 2 (b). In all cases studied here there is a monotonic decrease of the intensity with increasing temperature. The transition temperatures T_{CO} is tentatively identified with that temperature where the extrapolated intensity of the superstructure reflection at the Cu L_3 edge disappears. In

this way we obtain for $x = 0.125$ and 0.15 $T_{CO} = 80 \pm 10$ K and 70 ± 10 K, respectively. The lower T_{CO} with increasing x can be rationalized by a reduced stripe stability for doping concentrations away from $x = 1/8$. From the peak intensities at the $O\ K$ edge the transition temperature can be less well determined. The reason for this is that in this case, the signal to background ratio, especially at high temperatures, is rather low leading to large error bars.

The widths of the superstructure peaks at low temperatures derived from the fits are 4-8 times larger than the instrumental widths checked at the (001) Bragg peak. This means that the width is determined by a finite correlation length of the charge order. This correlation length is of the order of 85 and 100 lattice constants, a , and then decreases by about a factor of two before T_{CO} is reached. The finite widths at low temperatures indicate disorder due to quantum fluctuations or due to the potential of the dopant ions. A disorder caused by a deviation from the $1/8$ doping concentration (which is the ideal concentration for the traditional stripe picture) is less probable since at low temperatures there is no clear difference in the width for the two concentrations $x = 0.125$ and 0.15 .

More interestingly, the wave vector ϵ for the lattice distortion superstructure reflection increases between the two concentrations from 0.228 to 0.254. These values are perfectly in line with the general incommensurability curve of low-energy spin excitations $\epsilon/2$ versus x which for smaller x is determined by $\epsilon/2 = x$ and saturates above $x = 0.125$ [18]. From this excellent agreement we can conclude that the fluctuating magnetic stripes and the charge order, directly detected by RSXS, correspond to the same phenomenon. Furthermore, in a more conventional model stripes are often explained by a nesting between segments of the Fermi surface near the antinodal point with a nesting vector parallel to the Cu-O bond and being close to ϵ . However, in this model the nesting vector should decrease with increasing x while the present data show for the charge ordering an increase of ϵ with increasing x . This clearly excludes this simple nesting scenario for the explanation of stripes.

Comparing LESCO with other cuprates having an LTT phase, one realizes an interesting difference: the three transition temperatures $T_{LTT} = 125$ K, $T_{CO} = 80$ K and $T_{SO} = 45$ K (extrapolated from the value for $x = 0.15$ [11]) are distinctly different. Most importantly, the present RSXS data at the $O\ K$ edge prove the existence of a charge modulation well above T_{SO} . In other words, there is a large temperature range between 45 K and 80 K, where charge order exists without spin order. A similar observation was made for the sample with $x = 0.15$. This observation is at variance with the Hartree-Fock calculations [1], according to which the magnetic order drives the formation of charged stripes by a stabilization due to a magnetic interaction between the antifer-

romagnetic domains across the antiphase domain walls. Nonetheless, the magnetic and the charge order are expected to be coupled [19]. In the present study, this coupling is possibly indicated by small kinks in the temperature dependence of the intensity of the superstructure peak (see Fig. 2 (b), $O\ K$ and $Cu\ L_3$ data for $x = 0.125$) and in the widths (not shown) near T_{SO} . Furthermore, this view of the coupling between the two order parameters is supported by ESR studies revealing a sudden slowing down of the spin fluctuations which sets in close to T_{CO} [20]. Finally, it should be also noted that the difference in the transition temperatures cannot be explained by a different time resolution between RSXS and neutron scattering, since the same methods applied to LBCO did not yield a difference between T_{CO} and T_{SO} .

The results for LBCO, LNCO, and in particular LESCO clearly indicate that the charge stripes are stabilized by structural distortions that exist in the LTT phase. The corrugated CuO_2 planes create a pinning potential that favors the formation of stripe-like structures. Between T_{LTT} and T_{CO} , however, this potential is apparently not strong enough to stabilize static charge stripes.

Financial support by the DFG is appreciated by the IFW based researchers (Forschergruppe FOR 538) and by J.G.. The UBC based researchers acknowledge financial support from the Canadian granting organizations NSERC, CIFAR and CFI.

-
- [1] J. Zaanen and O. Gunnarsson, Phys. Rev. B **40**, 7391 (1989).
 - [2] R. J. Birgeneau et al., Phys. Rev. B **39**, 2868 (1989).
 - [3] M. Fujita et al., Phys. Rev. Lett. **88**, 167008 (2002).
 - [4] J. M. Tranquada, B. J. Sternlieb, J. D. Axe, Y. Nakamura, and S. Uchida, Nature **375**, 561 (1995).
 - [5] H. H. Klauss et al., Phys. Rev. Lett. **85**, 4590 (2000).
 - [6] M. Von Zimmermann et al., Europhysics Letters **41**, 629 (1998).
 - [7] P. Abbamonte et al., Science **297**, 581 (2002).
 - [8] P. Abbamonte et al., Nature Physics **1**, 155 (2005).
 - [9] P. Abbamonte, Phys. Rev. B **74**, 195113 (2006).
 - [10] J. M. Tranquada et al., Phys. Rev. B **54**, 7489 (1996).
 - [11] M. Hucker et al., Physica C (Amsterdam, Neth.) **460**, 170 (2007).
 - [12] B. Simovic et al., Phys. Rev. B **67**, 224508 (2003).
 - [13] H. Romberg et al., Phys. Rev. B **42**, 8768 (1990).
 - [14] C. T. Chen et al., Phys. Rev. Lett. **66**, 104 (1991).
 - [15] C. T. Chen et al., Phys. Rev. Lett. **68**, 2543 (1992).
 - [16] E. Pellegrin et al., Phys. Rev. B **47**, 3354 (1993).
 - [17] H. Eskes, M. B. J. Meinders, and G. A. Sawatzky, Phys. Rev. Lett. **67**, 1035 (1991).
 - [18] K. Yamada et al., Phys. Rev. B **57**, 6165 (1998).
 - [19] O. Zachar, S. A. Kivelson, and V. J. Emery, Phys. Rev. B **57**, 1422 (1998).
 - [20] V. Kataev et al., Phys. Rev. B **58**, R11876 (1998).